

High-water-content mouldable hydrogels by mixing clay and a dendritic molecular binder

Qigang Wang¹, Justin L. Mynar^{1,2}, Masaru Yoshida³, Eunji Lee⁴, Myongsoo Lee⁴, Kou Okuro¹, Kazushi Kinbara¹ & Takuzo Aida^{1,2}

With the world's focus on reducing our dependency on fossil-fuel energy, the scientific community can investigate new plastic materials that are much less dependent on petroleum than are conventional plastics. Given increasing environmental issues, the idea of replacing plastics with water-based gels, so-called hydrogels, seems reasonable. Here we report that water and clay (2–3 per cent by mass), when mixed with a very small proportion (<0.4 per cent by mass) of organic components, quickly form a transparent hydrogel. This material can be moulded into shape-persistent, free-standing objects owing to its exceptionally great mechanical strength, and rapidly and completely self-heals when damaged. Furthermore, it preserves biologically active proteins for catalysis. So far¹ no other hydrogels, including conventional ones formed by mixing polymeric cations and anions^{2,3} or polysaccharides and borax⁴, have been reported to possess all these features. Notably, this material is formed only by non-covalent forces resulting from the specific design of a telechelic dendritic macromolecule with multiple adhesive termini for binding to clay.

Hydrogels can be prepared using a covalent or a non-covalent approach. Most polymer hydrogels, covalently crosslinked, are brittle, have poor transparency and lack the ability to self-heal⁵. Double-network hydrogels, an early example of synthetic polymer hydrogels, solved the problem of brittleness⁶. More recently, hybridization of polymers with clay nanosheets (CNSs) has been shown to give mechanically tough and transparent hydrogels^{7–11}. However, the preparation of these materials uses *in situ* polymerization, which is lengthy and needs particular skills, and the products still lack the ability to self-heal.

We chose a non-covalent approach, owing to its advantages for easy, quick and reproducible preparation and the potential self-healing capability of the products¹². Our material consists of four components: water, CNSs, a dendritic macromolecule (*Gn*-binder; *n*, generation number; Fig. 1) and sodium polyacrylate (ASAP). Clay is a naturally occurring inorganic mineral salt with a layered structure, and is cheap to purchase¹³. On mixing with ASAP in water, CNSs, which are highly entangled with one another (Fig. 2a), are exfoliated and dispersed homogeneously owing to the mutual repulsion caused by a possible site-specific wrapping of their positive-charged edge parts¹³ with anionic ASAP (Fig. 2b). *Gn*-binder possesses two dendron units¹⁴, which are decorated with multiple guanidinium ion pendants on their peripheries (Fig. 1). A recently developed monodendron version of *Gn*-binder, referred to as 'molecular glue', can be used for non-covalent functionalization of proteins by means of salt-bridge formation between the guanidinium ion pendants and oxyanionic surface groups of proteins¹⁵. In the course of the above study, we noticed that this dendron strongly adheres to the surface of glass. This observation

motivated us to crosslink CNSs with *Gn*-binder (Fig. 2c), as the nanosheet surfaces are full of oxyanions¹³. Because *Gn*-binder carries adhesive dendron units at both termini of a long, hydrophilic PEG spacer (number-average molecular weight, $M_n = 10,650 \text{ g mol}^{-1}$), we expected that the nanosheets could be bound together to form a 3D network in water (Fig. 2c).

As described in Methods Summary, the hydrogel can be prepared quickly (3 min) by adding a very small proportion of G3-binder (0.15%) to a stirred aqueous solution of CNSs (2.0%) pretreated with ASAP (0.06%) (charge ratio (expressed in terms of the molar concentrations of charged groups), $[\text{CNSs (negative)}]/[\text{G3-binder (positive)}]/[\text{ASAP (negative)}] = 18.0/2.0/6.0 \text{ mM}$; Fig. 2a–h). The gel can also form without ASAP, but a decrease in mechanical strength results. Later addition of ASAP does not enhance the mechanical strength. Exfoliation and homogeneous dispersion of CNSs by ASAP, as visualized using cryogenic transmission electron microscopy (Fig. 2i, j), are essential for increasing the CNS effective surface area for binding with G3-binder. Although guanidine hydrochloride, used in place of *Gn*-binder under conditions identical to the above ($[\text{guanidinium ion}] = 2.0 \text{ mM}$), caused no gelation, G2- and even G1-binder induced hydrogelation. Also important is the telechelic structure of *Gn*-binder, as a monodendron version of G3-binder (PEG-G3-dendron; Fig. 1) did not cause gelation of water but precipitation of CNSs.

In Fig. 3a, the respective storage moduli, G' , and loss moduli, G'' , are shown for *Gn*-binders ($n = 1–3$; $[\text{guanidinium ion}] = 0.5 \text{ mM}$) as functions of angular frequency at a fixed strain, $\gamma = 1.0\%$. All three samples have a single plateau region in their dynamic moduli. The G' values have a substantial elastic response and are always larger than the G'' values over the entire range of frequencies. Among the three binders, G3-binder gives a hydrogel with the greatest G' value, suggesting a multivalent effect, as discussed previously for covalently crosslinked hydrogels^{16,17}. As shown in Fig. 3c, the G' values depend on the amount of CNS. For example, by using 5.0% CNS in conjunction with 0.38% G3-binder and 0.15% ASAP, a G' value of 0.5 MPa was achieved, which is the largest among those reported for supramolecular hydrogels¹. Although the systems without ASAP show the same trend in mechanical strength (Fig. 3b, d), pretreatment of CNSs with ASAP causes the G' value to increase by a factor of up to six.

As shown in Supplementary Fig. 1 (2.0% CNS, 0.15% G3-binder, 0.06% ASAP), the hydrogelation also takes place on heating but occurs more slowly as the temperature increases. Nevertheless, the mechanical properties of the hydrogels once formed hardly depend on the temperature (Supplementary Figs 2 and 3). At temperatures of $\geq 80^\circ\text{C}$, bubbles of water vapour are generated inside the hydrogel owing to a 'boiling-stone' effect of CNSs (Supplementary Fig. 4). The

¹Department of Chemistry and Biotechnology, School of Engineering, The University of Tokyo, 7-3-1 Hongo, Bunkyo-ku, Tokyo 113-8656, Japan. ²ERATO-SORST Nanospace Project, Japan Science and Technology Agency, National Museum of Emerging Science and Innovation, 2-41 Aomi, Koto-ku, Tokyo 135-0064, Japan. ³Nanotechnology Research Institute, National Institute of Advanced Industrial Science and Technology, 1-1-1 Higashi, Tsukuba, Ibaraki 305-8565, Japan. ⁴Center for Supramolecular Nano-Assembly and Department of Chemistry, Seoul National University, 599 Kwanak-ro, Seoul 151-747, Korea.

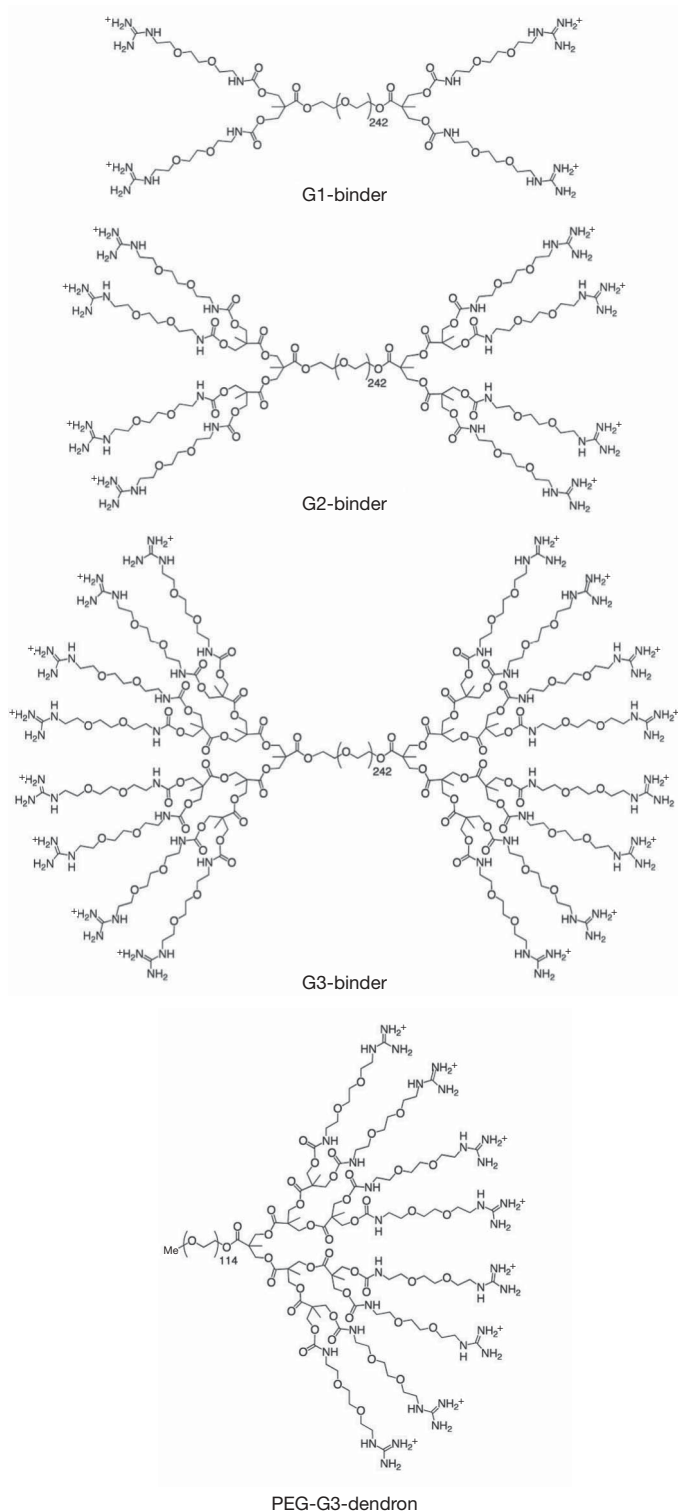


Figure 1 | Schematic structures of dendritic *Gn*-binders ($n = 1-3$) and a monodendron analogue of *G3*-binder (PEG-G3-dendron). Owing to multivalency provided by the dendronized structure, the guanidinium ion groups strongly adhere to CNSs dispersed by sodium polyacrylate. *Gn*-binders are telechelic and crosslink CNSs together to form a three-dimensional (3D) network in water. PEG, polyethylene glycol; Me, CH_3 .

overall thermal properties of the hydrogel indicate that the hydrogelation takes place by kinetic trapping of the 3D network structure formed by the adhesion of *G3*-binder to CNSs. When the hydrogelation is conducted during heating, the dendritic branches of *G3*-binder may adopt a folded conformation as a result of dehydration, causing the 3D network to form slowly.

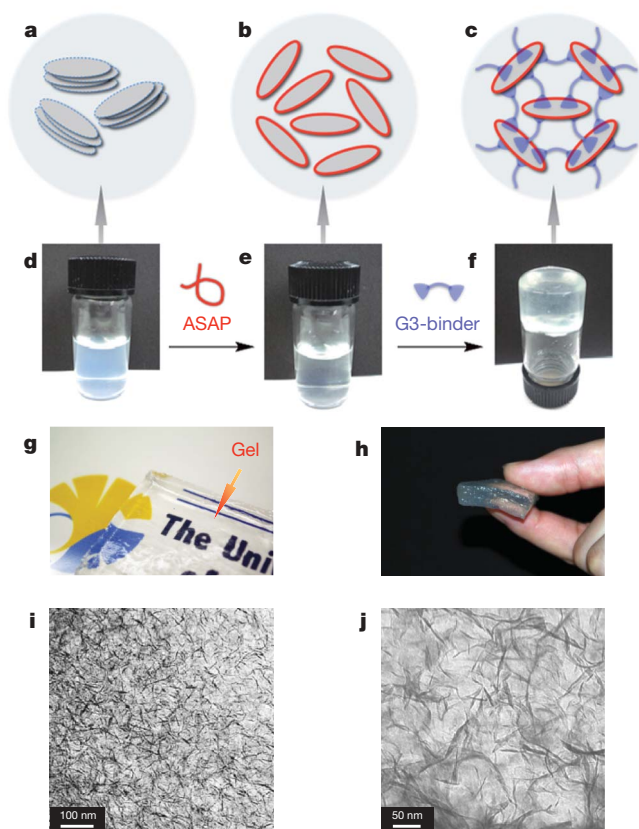


Figure 2 | Non-covalent preparation of hydrogels.

a–c, Proposed mechanism for hydrogelation. CNSs, entangled with one another (a), are dispersed homogeneously by interaction of their positive-charged edge parts with anionic ASAP (b). Upon addition of *Gn*-binder, exfoliated CNSs are crosslinked to develop a 3D network (c). **d–f,** Optical images of an aqueous suspension of CNSs (d), an aqueous dispersion of CNSs and ASAP (e) and a physical gel upon addition of *G3*-binder to the dispersion (f). **g, h,** The gel is transparent (g) and free standing (h). **i, j,** Cryogenic transmission electron microscopy micrographs of the hydrogel, showing homogeneously dispersed CNSs on different scales.

As shown in Fig. 3e, strain amplitude sweeps of the samples demonstrated an elastic response typical of hydrogels. The G' value of the toughest material, which contained 5.0% CNS, 0.38% *G3*-binder and 0.15% ASAP, rapidly decreases above the critical strain region ($\gamma = 9.0\%$), indicating a collapse of the gel state to a quasi-liquid state. We note that this sample exhibits very rapid recovery of its mechanical properties after a large-amplitude oscillatory breakdown, known as thixotropy (Fig. 3f). Under the application of a large-amplitude oscillatory force ($\gamma = 100\%$; frequency, $\omega = 6.0 \text{ rad s}^{-1}$ (1.0 Hz)), the G' value decreases from 0.5 MPa to 5 kPa, resulting in a quasi-liquid state ($\tan \delta \equiv G''/G' \approx 3.0-4.0$). However, when the amplitude is decreased ($\gamma = 0.1\%$) at the same frequency (1.0 Hz), G' immediately recovers its initial value and the system returns to a quasi-solid state ($\tan \delta \approx 0.4-0.5$). The gel without ASAP is not free-standing. Accordingly, the yield stress, estimated from the oscillatory shear stress applied at the starting point of the decay of the storage modulus (G') in the strain-sweep profile, is less than 100 Pa, which is much smaller than that of the hydrogel with ASAP ($>5,000 \text{ Pa}$).

Copolyptide hydrogels¹⁸, which were early examples of self-healing hydrogels, are mechanically much weaker (G' values $<1 \text{ kPa}$) and, after a shear force is applied, require more than 1 h for G' to recover its initial value. Although oligomeric electrolyte hydrogels¹⁹ have the ability to recover with a speed comparable to that of our hydrogel, their G' values are estimated to be 50 times smaller. Our hydrogel has both a large mechanical strength and a fast-recovery capability. The first feature may result largely from the mechanical toughness of CNSs, the main component of the 3D network in our material. Furthermore, the network

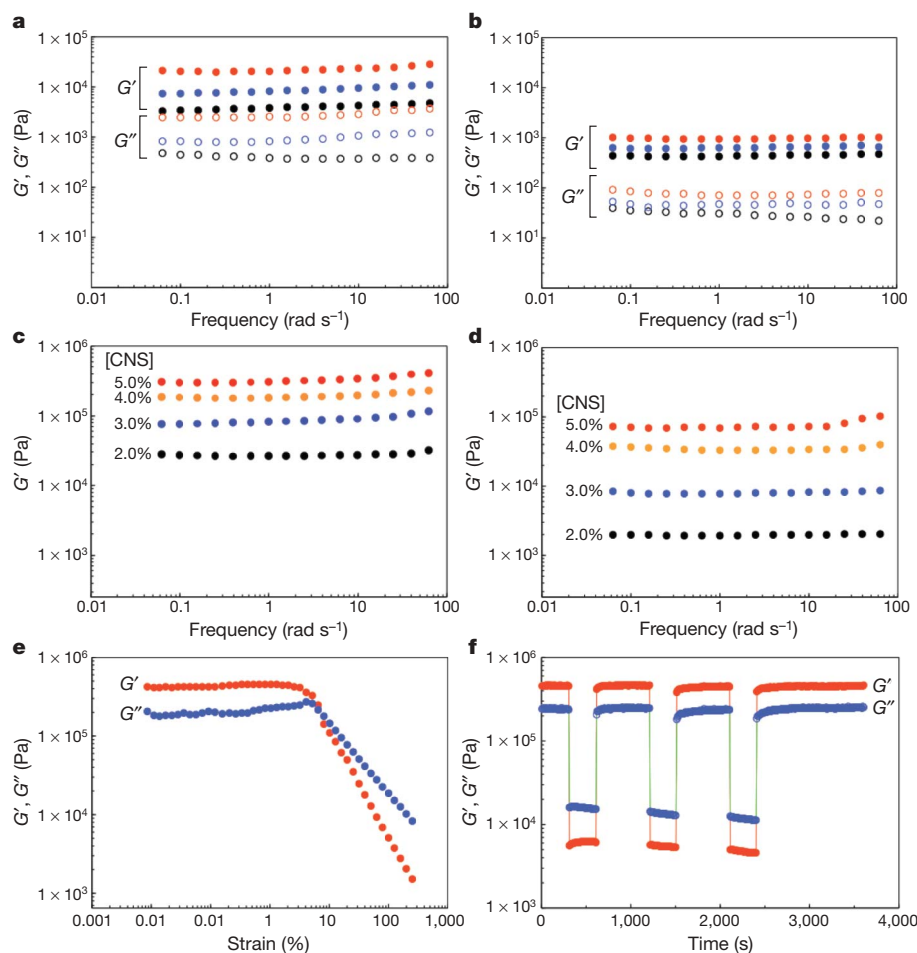


Figure 3 | Rheological properties (20 °C) of hydrogels. **a, b,** G' and G'' values of hydrogels (2.0% CNS, G3-binder ($n = 1$ (black), $n = 2$ (blue), $n = 3$ (red))) for [guanidinium ion] = 0.5 mM with (**a**) and without (**b**) 0.06% ASAP, on frequency sweep (from 0.06 to 60 rad s^{-1}). **c, d,** G' values of hydrogels (2.0–5.0% CNS, G3-binder) at weight ratios CNS/G3-binder/

ASAP of 1.0/0.075/0.03 (**c**) and 1.0/0.075/0 (**d**), on frequency sweep (from 0.06 to 60 rad s^{-1}). **e, f,** G' and G'' values of a hydrogel (5.0% CNS, 0.38% G3-binder, 0.15% ASAP) on strain sweep (**e**) and in continuous step strain measurements (**f**).

structure is formed simply by attaching the guanidinium ion pendants of G3-binder to the exfoliated CNS surfaces, so the recovery process does not involve reassembly of organic components and is therefore quick.

Freshly cut surfaces of our hydrogels adhere to each other. As shown in Fig. 4a, we constructed a 3.5-cm-long bridge by connecting seven blocks. First two building blocks, both composed of 96.7% water, 3.0% CNS, 0.21% G3-binder and 0.09% ASAP, were sliced with a razor to expose fresh surfaces. Then the blocks were pushed together so that these surfaces came into contact with each other. New blocks were sliced and added in the same way until the bridge spanned a desired length. The resulting bridge is strong enough to hold when suspended horizontally, between two posts (Fig. 4a), or vertically, from a needle (Fig. 4b). If the blocks are not cut to obtain fresh surfaces, the fusion does not take place. Moreover, if the blocks are cut but left for more than a minute alone, they do not adhere to each other. We found that the freshly cut surfaces, essential for the adhesion of the blocks, are hydrophilic, as a deposited water droplet spread over a cut surface immediately but remained beaded on an uncut surface (Supplementary Fig. 5).

Unlike other supramolecular hydrogels, our material remains shape persistent even when immersed in an organic solvent such as tetrahydrofuran (THF). For example, a heart-shaped object (3.0 g), moulded using 97.8% water, 2.0% CNS, 0.14% G3-binder and 0.06% ASAP (Fig. 4c), was immersed in THF (9.0 g) for 6 h. When this procedure was repeated twice, the water in the moulded object, as determined by gas chromatography, was replaced with THF almost

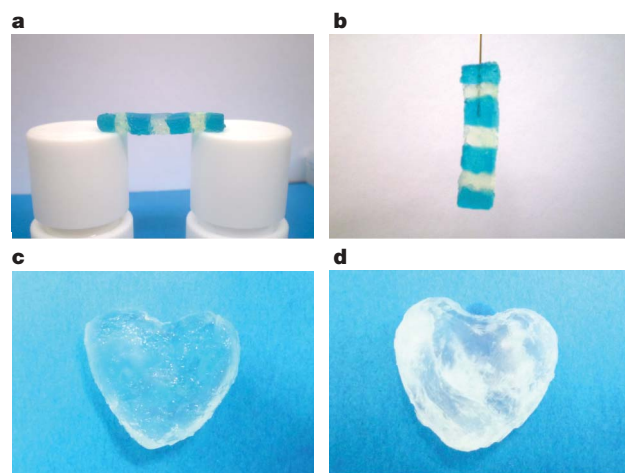


Figure 4 | Shape-persistent, free-standing macroscopic objects moulded from a hydrogel. Hydrogels with and without 0.01% methylene blue (for visibility) were prepared using 3.0% CNS, 0.21% G3-binder and 0.09% ASAP, and cut into small blocks. **a, b,** A bridge constructed by connecting together seven hydrogel blocks can be suspended horizontally (**a**) and held vertically (**b**). Diffusion of methylene blue from one block to the other hardly takes place, probably because of its adhesion to the CNS surfaces. **c, d,** Pictures of a heart-shaped hydrogel object before (**c**) and after (**d**) being immersed for 6 h three times in fresh THF at 20 °C.

completely. However, the gel network, even after the complete exchange of water for THF, maintained its form and integrity (Fig. 4d). Such an organogel cannot be formed directly from THF, CNSs and *Gn*-binder, regardless of the presence of ASAP.

Whereas the preparation of most hydrogels generally relies on repeated heating/cooling cycles^{20–24}, ultrasonication²⁵, *in situ* polymerizations^{6–11,26} or crosslinking reactions²⁷, our hydrogel can readily be prepared by mixing the three components in water at room temperature. We also found that the hydrogel lasts for a long time in salty water and also under moderately acidic or basic conditions (pH 4.0–10.0; Supplementary Fig. 6). Importantly for applications, even brine can be gelled by the addition of CNSs, G3-binder and ASAP, and G' remains almost unchanged, relative to the salt-free value, for $[NaCl] = 0–10$ mM (Supplementary Fig. 7). Because it is composed mostly of water, our self-standing hydrogel, although much tougher than other supramolecular hydrogels used for immobilizing enzymes^{28–30}, could incorporate and maintain biologically active proteins. As the first step towards this goal, we prepared a myoglobin-containing hydrogel by mixing CNSs (2.0%), G3-binder (0.04%) and ASAP (0.06%) in an aqueous solution of myoglobin (5.0 μ M; Supplementary Fig. 8). No denaturation of the myoglobin was observed for at least one week, judging from its absorption spectral feature. Myoglobin is known to catalyse oxidation of *o*-phenylenediamine with H_2O_2 . To investigate whether our tough hydrogel can provide a proper environment for catalysis, the myoglobin-containing hydrogel was added at 20 °C to a phosphate buffer solution of a mixture of *o*-phenylenediamine and H_2O_2 . As shown in Fig. 5, myoglobin in the hydrogel retains an activity of ~71% relative to free myoglobin, despite the fact that G3-binder alone considerably reduces the activity (to 35%), probably by adhesion to the protein¹⁵. Thus, our shape-persistent hydrogel can transport biological activities.

Our material is not only environmentally friendly, readily prepared and self-healing (because it is non-covalent), but is also mouldable into various free-standing shapes owing to its large mechanical strength. Furthermore, simple moulded objects can be fused together to construct more complex architectures. By connecting together several blocks with different enzymatic activities, a certain reaction sequence might be designed. Our hydrogel contradicts the preconception that materials held together by supramolecular forces and

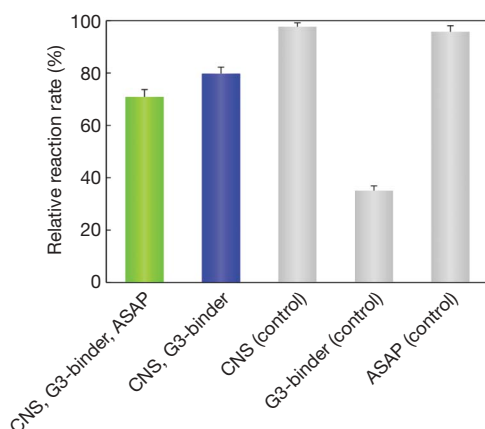


Figure 5 | Catalytic activities of myoglobin in hydrogels. Hydrogels were prepared by mixing 2.0% CNS with 0.04% G3-binder in a 5.0 μ M aqueous solution of myoglobin with (green) and without (blue) 0.06% ASAP, and suspended in phosphate buffer (pH 7.4) containing *o*-phenylenediamine (10 mM). Then an aqueous solution of H_2O_2 was injected ($[myoglobin]/[o\text{-phenylenediamine}]/[H_2O_2] = 0.5 \mu\text{M}/10 \text{ mM}/25 \text{ mM}$), and a change in absorption at 420 nm due to 2,3-diamino-5,10-dihydrophenazine (product) was monitored at 20 °C. Error bars, s.d. ($N = 3$). All controls (grey) were measured under identical conditions. In every case, the reaction displayed a zero-order kinetics (linear correlation coefficient, $R > 0.99$).

mostly composed of water are weak, and may provide many interesting applications.

METHODS SUMMARY

In a typical example of hydrogelation, we added 1.0 ml of an aqueous solution of ASAP (3.0 mg) at 20 °C to a stirred suspension of CNSs (100 mg) in water (3.75 ml). After 10 min, the suspension turned to a clear solution owing to exfoliation of CNSs (Fig. 2b, e). Then we added 0.25 ml of an aqueous solution of G3-binder (7.5 mg) dropwise while stirring. The mixture became completely stiff (Fig. 2c, f) within only 3 min, forming a transparent, self-standing material (Fig. 2g, h). We prepared other hydrogels similarly, but at different temperatures such as 10, 40, 50, 60, 70 and 80 °C (Supplementary Fig. 1). We measured rheological properties of the hydrogels (Fig. 3), including those prepared on heating (Supplementary Fig. 2), at 25 °C using a TA Instruments ARES-RFS controlled-strain rheometer, with a 25-mm-diameter para-plate attached to a transducer. The gap at the apex of the para-plate was set to be 0.5 mm. The samples were placed between the para-plate and the platform with special care to avoid evaporation of water. To investigate the recovery properties of the samples in response to applied shear forces, we used the following 1-h programmed procedure (applied shear force, expressed in terms of strain; duration in parentheses): 0.1% (300 s) $\rightarrow$ 100% (300 s) $\rightarrow$ 0.1% (600 s) $\rightarrow$ 100% (300 s) $\rightarrow$ 0.1% (600 s) $\rightarrow$ 100% (300 s) $\rightarrow$ 0.1% (1,200 s). We investigated temperature dependencies of the rheological properties of a hydrogel prepared at 20 °C, using a temperature-change programme: 25 °C $\rightarrow$ 10 °C $\rightarrow$ 70 °C $\rightarrow$ 25 °C, changing at a rate of 10 °C min⁻¹ (Supplementary Fig. 3). The hydrogel prepared at 20 °C was heated to a designated temperature (60, 70 or 80 °C) for 10 min and cooled to 20 °C to investigate its macroscopic thermal stability (Supplementary Fig. 4).

Received 27 May; accepted 17 October 2009.

- Hirst, A. R., Escuder, B., Miravet, J. F. & Smith, D. K. High-tech applications of self-assembling supramolecular nanostructured gel-phase materials: from regenerative medicine to electronic devices. *Angew. Chem. Int. Edn* **47**, 8002–8018 (2008).
- Marsich, E. et al. Alginate/lactose-modified chitosan hydrogels: a bioactive biomaterial for chondrocyte encapsulation. *J. Biomed. Mater. Res. A* **84A**, 364–376 (2007).
- Crompton, K. E. et al. Polylysine-functionalised thermoresponsive chitosan hydrogel for neural tissue engineering. *Biomaterials* **28**, 441–449 (2007).
- Pezron, E., Ricard, A., Lafuma, F. & Audebert, R. Reversible gel formation induced by ion complexation. 1. Borax-galactomannan interactions. *Macromolecules* **21**, 1121–1125 (1988).
- Peppas, N. A., Huang, Y., Torres-Lugo, M., Ward, J. H. & Zhang, J. Physicochemical, foundations and structural design of hydrogels in medicine and biology. *Annu. Rev. Biomed. Eng.* **2**, 9–29 (2000).
- Gong, J. P., Katsuyama, Y., Kurokawa, T. & Osada, Y. Double-network hydrogels with extremely high mechanical strength. *Adv. Mater.* **15**, 1155–1158 (2003).
- Haraguchi, K. & Takehisa, T. Nanocomposite hydrogel: a unique organic-inorganic network structure with extraordinary mechanical, optical, and swelling/deswelling properties. *Adv. Mater.* **14**, 1120–1124 (2002).
- Liu, Y. et al. High clay content nanocomposite hydrogels with surprising mechanical strength and interesting deswelling kinetics. *Polymer* **47**, 1–5 (2006).
- Okada, A. & Usuki, A. Twenty years of polymer-clay nanocomposites. *Macromol. Mater. Eng.* **291**, 1449–1476 (2006).
- Okay, O. & Oppermann, W. Polyacrylamide-clay nanocomposite hydrogel: rheological and light scattering characterization. *Macromolecules* **40**, 3378–3387 (2007).
- Li, P., Siddaramaiah, Kim, N. H., Yoo, G. & Lee, J. Poly(acrylamide/laponite) nanocomposite hydrogels: swelling and cationic dye adsorption properties. *J. Appl. Polym. Sci.* **111**, 1786–1798 (2009).
- Sijbesma, R. P. et al. Reversible polymers formed from self-complementary monomers using quadruple hydrogen bonding. *Science* **278**, 1601–1604 (1997).
- Rockwood Additives Ltd. *Laponite in Personal Care Products*. Tech. Bull. L211/O1g (1990).
- Ihre, H., Padilla De Jesus, O. L. & Fréchet, J. M. J. Fast and convenient divergent synthesis of aliphatic ester dendrimers by anhydride coupling. *J. Am. Chem. Soc.* **123**, 5908–5917 (2001).
- Okuro, K., Kinbara, K., Tsumoto, K., Ishii, N. & Aida, T. Molecular glues carrying multiple guanidinium ion pendants via oligoether spacer: stabilization of microtubules against depolymerization. *J. Am. Chem. Soc.* **131**, 1626–1627 (2009).
- Carnahan, M. A., Middleton, C., Kim, J., Kim, T. & Grinstaff, M. W. Hybrid dendritic-linear polyester-ethers for *in situ* photopolymerization. *J. Am. Chem. Soc.* **124**, 5291–5293 (2002).
- Wathier, M., Jung, P. J., Carnahan, M. A., Kim, T. & Grinstaff, M. W. Dendritic macromers as *in situ* polymerizing biomaterials for securing cataract incisions. *J. Am. Chem. Soc.* **126**, 12744–12745 (2004).
- Nowak, A. P. et al. Rapidly recovering hydrogel scaffolds from self-assembling diblock copolypeptide amphiphiles. *Nature* **417**, 424–428 (2002).

19. Yoshida, M. *et al.* Oligomeric electrolyte as a multifunctional gelator. *J. Am. Chem. Soc.* **129**, 11039–11041 (2007).
20. Xing, B. G. *et al.* Hydrophobic interaction and hydrogen bonding cooperatively confer a vancomycin hydrogel: a potential candidate for biomaterials. *J. Am. Chem. Soc.* **124**, 14846–14847 (2002).
21. Silva, G. A. *et al.* Selective differentiation of neural progenitor cells by high-epitope density nanofibers. *Science* **303**, 1352–1355 (2004).
22. Sreenivasachary, N. & Lehn, J. M. Gelation-driven component selection in the generation of constitutional dynamic hydrogels based on guanine-quartet formation. *Proc. Natl Acad. Sci. USA* **102**, 5938–5943 (2005).
23. Jayawarna, V. *et al.* Nanostructured hydrogels for three-dimensional cell culture through self-assembly of fluorenylmethoxycarbonyl-dipeptides. *Adv. Mater.* **18**, 611–614 (2006).
24. Schnepf, Z. A. C., Gonzalez-McQuire, R. & Mann, S. Hybrid biocomposites based on calcium phosphate mineralization of self-assembled supramolecular hydrogels. *Adv. Mater.* **18**, 1869–1872 (2006).
25. Rokita, B., Rosiak, J. M. & Ulanski, P. Ultrasound-induced cross-linking and formation of macroscopic covalent hydrogels in aqueous polymer and monomer solutions. *Macromolecules* **42**, 3269–3274 (2009).
26. Dong, L., Agarwal, A. K., Beebe, D. J. & Jiang, H. R. Adaptive liquid microlenses activated by stimuli-responsive hydrogels. *Nature* **442**, 551–554 (2006).
27. Ladet, S., David, L. & Domard, A. Multi-membrane hydrogels. *Nature* **452**, 76–79 (2008).
28. Kiyonaka, S. *et al.* Semi-wet peptide/protein array using supramolecular hydrogel. *Nature Mater.* **3**, 58–64 (2004).
29. Wang, Q. G., Yang, Z. M., Wang, L., Ma, M. L. & Xu, B. Molecular hydrogel-immobilized enzymes exhibit superactivity and high stability in organic solvents. *Chem. Commun.* **10**, 1032–1034 (2007).
30. Das, A. K., Collins, R. & Ulijn, R. V. Exploiting enzymatic (reversed) hydrolysis in directed self-assembly of peptide nanostructures. *Small* **4**, 279–287 (2008).

Supplementary Information is linked to the online version of the paper at www.nature.com/nature.

Acknowledgements Q.W. thanks the Japan Society for the Promotion of Science postdoctoral fellowship for foreign researchers. We thank Y. Arakawa for his support for the synthesis of PEG-G3-dendron.

Author Contributions Q.W. synthesized *Gn*-binders and analysed the properties of hydrogels; K.O. and K.K. noticed adhesion of guanidinium-ion-appended dendrimers to glass surfaces; M.Y. assisted the rheological studies; E.L. and M.L. performed cryogenic transmission electron microscopy; and T.A., J.L.M. and Q.W. designed the study, analysed the data and wrote the paper.

Author Information Reprints and permissions information is available at www.nature.com/reprints. The authors declare no competing financial interests. Correspondence and requests for materials should be addressed to T.A. (aida@macro.t.u-tokyo.ac.jp) or J.L.M. (jmynar@berkeley.edu).